

# Refinement of waste phosphogypsum from Prahovo, Serbia: characterization and assessment of application in civil engineering

Josip Išek, Lazar Kaluđerović, Nikola Vuković, Maja Milošević, Ivana Vukašinović, Zorica Tomić



Дигитални репозиторијум Рударско-геолошког факултета Универзитета у Београду

[ДР РГФ]

Refinement of waste phosphogypsum from Prahovo, Serbia: characterization and assessment of application in civil engineering | Josip Išek, Lazar Kaluđerović, Nikola Vuković, Maja Milošević, Ivana Vukašinović, Zorica Tomić | Clay Minerals | 2020 | |

10.1180/clm.2020.11

<http://dr.rgf.bg.ac.rs/s/repo/item/0008252>


Дигитални репозиторијум Рударско-геолошког факултета Универзитета у Београду омогућава приступ издањима Факултета и радовима запослених доступним у слободном приступу. - Претрага репозиторијума доступна је на [www.dr.rgf.bg.ac.rs](http://www.dr.rgf.bg.ac.rs)

The Digital repository of The University of Belgrade Faculty of Mining and Geology archives faculty publications available in open access, as well as the employees' publications. - The Repository is available at: [www.dr.rgf.bg.ac.rs](http://www.dr.rgf.bg.ac.rs)



## Article

# Refinement of waste phosphogypsum from Prahovo, Serbia: characterization and assessment of application in civil engineering

Josip I. Išek<sup>1</sup>, Lazar M. Kaluđerović<sup>2\*</sup> , Nikola S. Vuković<sup>3</sup>, Maja Milošević<sup>1</sup>, Ivana Vukašinić<sup>2</sup> and Zorica P. Tomić<sup>2</sup>

<sup>1</sup>University of Belgrade, Faculty of Mining and Geology, Đušina 7, 11000 Belgrade, Serbia; <sup>2</sup>University of Belgrade, Faculty of Agriculture, Nemanjina 6, 11080 Belgrade, Serbia and <sup>3</sup>NTC NIS-Naftagas Ltd, Narodnog fronta 12, 21000 Novi Sad, Serbia

### Abstract

Two samples collected from the phosphogypsum deposits of the chemical products industry Elixir Prahovo (Serbia) were subjected to a recrystallization experiment performed over several repeated cycles. In these tests, phosphogypsum was separated into recrystallized (purified) gypsum, insoluble residue and supernatant. Both raw phosphogypsum and recrystallized gypsum were examined using inductively coupled plasma optical emission spectrometry, X-ray diffraction and scanning electron microscopy with energy-dispersive spectrometry. The activity concentrations of <sup>238</sup>U, <sup>235</sup>U, <sup>226</sup>Ra, <sup>210</sup>Pb, <sup>232</sup>Th and <sup>40</sup>K were investigated using  $\gamma$ -ray spectrometry. Based on the activity concentration results, a number of radiometric parameters were calculated for the original and recrystallized phosphogypsum (*i.e.* radium equivalent activity,  $\gamma$  indices for construction materials,  $\alpha$  index and external and internal hazard indices). Raw phosphogypsum samples showed greater mean activity concentration levels of <sup>238</sup>U and <sup>226</sup>Ra than the international recommended limits, while the recrystallized gypsum demonstrated notably lower activity concentrations for these two isotopes. The activity concentration of <sup>226</sup>Ra in recrystallized gypsum is  $\sim 6$  times lower than in raw phosphogypsum. Therefore, recrystallized gypsum does not present a radiation hazard when used as a building material, while raw phosphogypsum meets the requirements only for road construction materials.

**Keywords:**  $\gamma$ -spectrometry, brushite, chukhrovite, phosphogypsum, radionuclides, recrystallization

(Received 12 December 2019; revised 4 April 2020; Accepted Manuscript online: 28 April 2020; Associate Editor: Asuman Turkmenoglu)

Phosphogypsum is a waste product of the phosphoric acid manufacturing process. It is produced in the form of a fine powder with a large calcium sulfate content. This process produces  $\sim 5$  tons of phosphogypsum for every ton of phosphoric acid manufactured (Hammam *et al.*, 2013).

According to the International Atomic Energy Agency (IAEA), annual phosphogypsum production worldwide is  $\sim 160$  million tons, of which 50 million tons are produced in China and 40 million tons are produced in the USA (IAEA, 2013). Raw phosphogypsum is generally yellowish, which, along with its greyish grains, defines it as a low-grade gypsum material in traditional applications, such as in cements and mortars (Costa *et al.*, 2019). Primary impurities in phosphogypsum are phosphates, fluorides, organic substances and alkali metals (Hua *et al.*, 2016; Walawalkar *et al.*, 2016).

The commercial use of phosphogypsum in the areas of agriculture, road construction, the cement industry and the manufacturing processes of other building materials is limited by the presence of the significant quantities of natural radionuclides, such as U, Ra and Th (Pérez-López *et al.*, 2016). However, there is still a lack of information regarding the potential release of metals and radionuclides during the lifetime of certain applications (Hua *et al.*, 2016; Cánovas, 2018).

Naturally occurring radionuclides are the main sources of human exposure to ionizing radiation. The redistribution of these radionuclides in the environment through human activities should be considered for inclusion within the scope of regulation as naturally occurring radioactive materials (IAEA, 2013). Phosphate minerals, as a source of phosphogypsum, have significant natural radioactivity, originating from natural radionuclides that are members of the <sup>238</sup>U and <sup>232</sup>Th decay series. Sedimentary phosphate rocks contain high concentrations of uranium and low concentrations of thorium, while igneous rocks have lower concentrations of uranium and higher concentrations of thorium and rare earth elements (Moreira *et al.*, 2018). The concentration of <sup>238</sup>U varies according to the mineral origin, from 260 to 1860 Bq kg<sup>-1</sup> for apatite and from 460 to 640 Bq kg<sup>-1</sup> for phosphorite (Saeuie, 1998).

Through the manufacturing process,  $\sim 80\%$  of <sup>226</sup>Ra, 14% of <sup>238</sup>U and 30% of <sup>232</sup>Th tend to be enriched in phosphogypsum, and the rest remains in phosphoric acid (Jung *et al.*, 2017). This is due to the extremely low solubility product of RaSO<sub>4</sub> ( $3.66 \times 10^{-11}$ ). Thus, large amounts of Ra are concentrated in phosphogypsum, while U and Th are transferred into the phosphoric acid. Through these chemical processes, the secular equilibrium between the specific decay series breaks down.

The main objective of this study was to extract and characterize purified gypsum, as well as insoluble impurities from raw phosphogypsum. A secondary objective was to examine natural radionuclide activities in samples of phosphogypsum from a waste deposit before and after the recrystallization process. The

\*E-mail: lazark@agrif.bg.ac.rs

**Cite this article:** Išek JI, Kaluđerović LM, Vuković NS, Milošević M, Vukašinić I, Tomić ZP (2020). Refinement of waste phosphogypsum from Prahovo, Serbia: characterization and assessment of application in civil engineering. *Clay Minerals* 55, 63–70. <https://doi.org/10.1180/clm.2020.11>



Fig. 1. Location of the phosphogypsum landfill.

results obtained in this study may promote the potential utilization of purified phosphogypsum in the construction industry and in agriculture.

## Materials and methods

### Samples

The raw phosphogypsum samples were obtained from the waste landfills of the chemical company Elixir Prahovo (Serbia) (Fig. 1), which produces 165 000 tons of phosphoric acid annually (Elixir Prahovo, 2018). Several subsamples were collected from two different points at the landfill and were mixed to produce two composite samples. The samples were dried at 50°C for 48 h and sieved through a 2 mm sieve. These raw samples, labelled as PG1 and PG2, were subjected to chemical, phase and morphological characterization, as well as activity concentration determination.

Sample PG1, due to its higher activity concentration of  $^{238}\text{U}$ , was further subjected to the recrystallization process (Fig. 2). A total of 10 g of the sample was mixed with 2 L of distilled water in a beaker. Using a magnetic stirrer, the mixture was stirred for 2 h at  $\sim 45^\circ\text{C}$ , allowed to settle for 2 h at the same temperature and filtered through filter paper. The filtrate was then heated in another beaker at  $90^\circ\text{C}$ , stirred with a magnetic stirrer for 1 h and allowed to settle for 7 h at the same temperature, allowing excess calcium sulfate to crystallize. Recrystallized gypsum was filtered and washed with boiling distilled water. The supernatant liquid was mixed with the phosphogypsum from the first beaker. This cycle was repeated several times until the PG1 sample was reduced to an insoluble residue. In this manner, the phosphogypsum was separated into recrystallized gypsum (PG1P), insoluble residue (PG1R) and

supernatant. Using the available literature data and general knowledge of the phosphoric acid production process, the most significant impurities identified in raw phosphogypsum were detrital quartz (by volume),  $\text{RaSO}_4$  (by radioactivity) and ferric oxyhydroxides affecting the colour (e.g. Pérez-López *et al.*, 2016; Jung *et al.*, 2017). As all of these components are essentially insoluble in water, in contrast to calcium sulfate, the recrystallization procedure was employed to improve gypsum purity, radioactivity level and colour.

The retrograde solubility of gypsum in water (slowly increasing from 0 to  $40^\circ\text{C}$ , with a subsequent decrease from 40 to  $100^\circ\text{C}$ ; Rolnick, 1954; Amjad, 1988; Azimi, 2010) was used as a driving mechanism for the recrystallization process. The mass balance of the recrystallization experiment for the PG1 sample is as follows: the yield of purified gypsum (PG1P) was 90.50%, with 4.29% of insoluble residue (PG1R) and 5.21% of the original mass in the supernatant.

Sample PG1P was also subjected to chemical analysis, phase and morphological characterization and activity concentration determination, while sample PG1R was subjected only to chemical characterization using scanning electron microscopy with energy-dispersive spectrometry (SEM-EDS).

### Scanning electron microscopy

SEM-EDS analysis was performed using a JEOL JSM-IT300 SEM coupled with an Oxford Instruments XMax 50  $\text{mm}^2$  silicon drift detector energy-dispersive spectrometer, in high-vacuum mode, at an accelerating voltage of 20 kV and a probe current of  $\sim 0.1$  nA. For SEM imaging, the samples were coated with gold. The EDS elemental analyses were conducted using low magnification (50 $\times$ ) on carbon-coated samples.

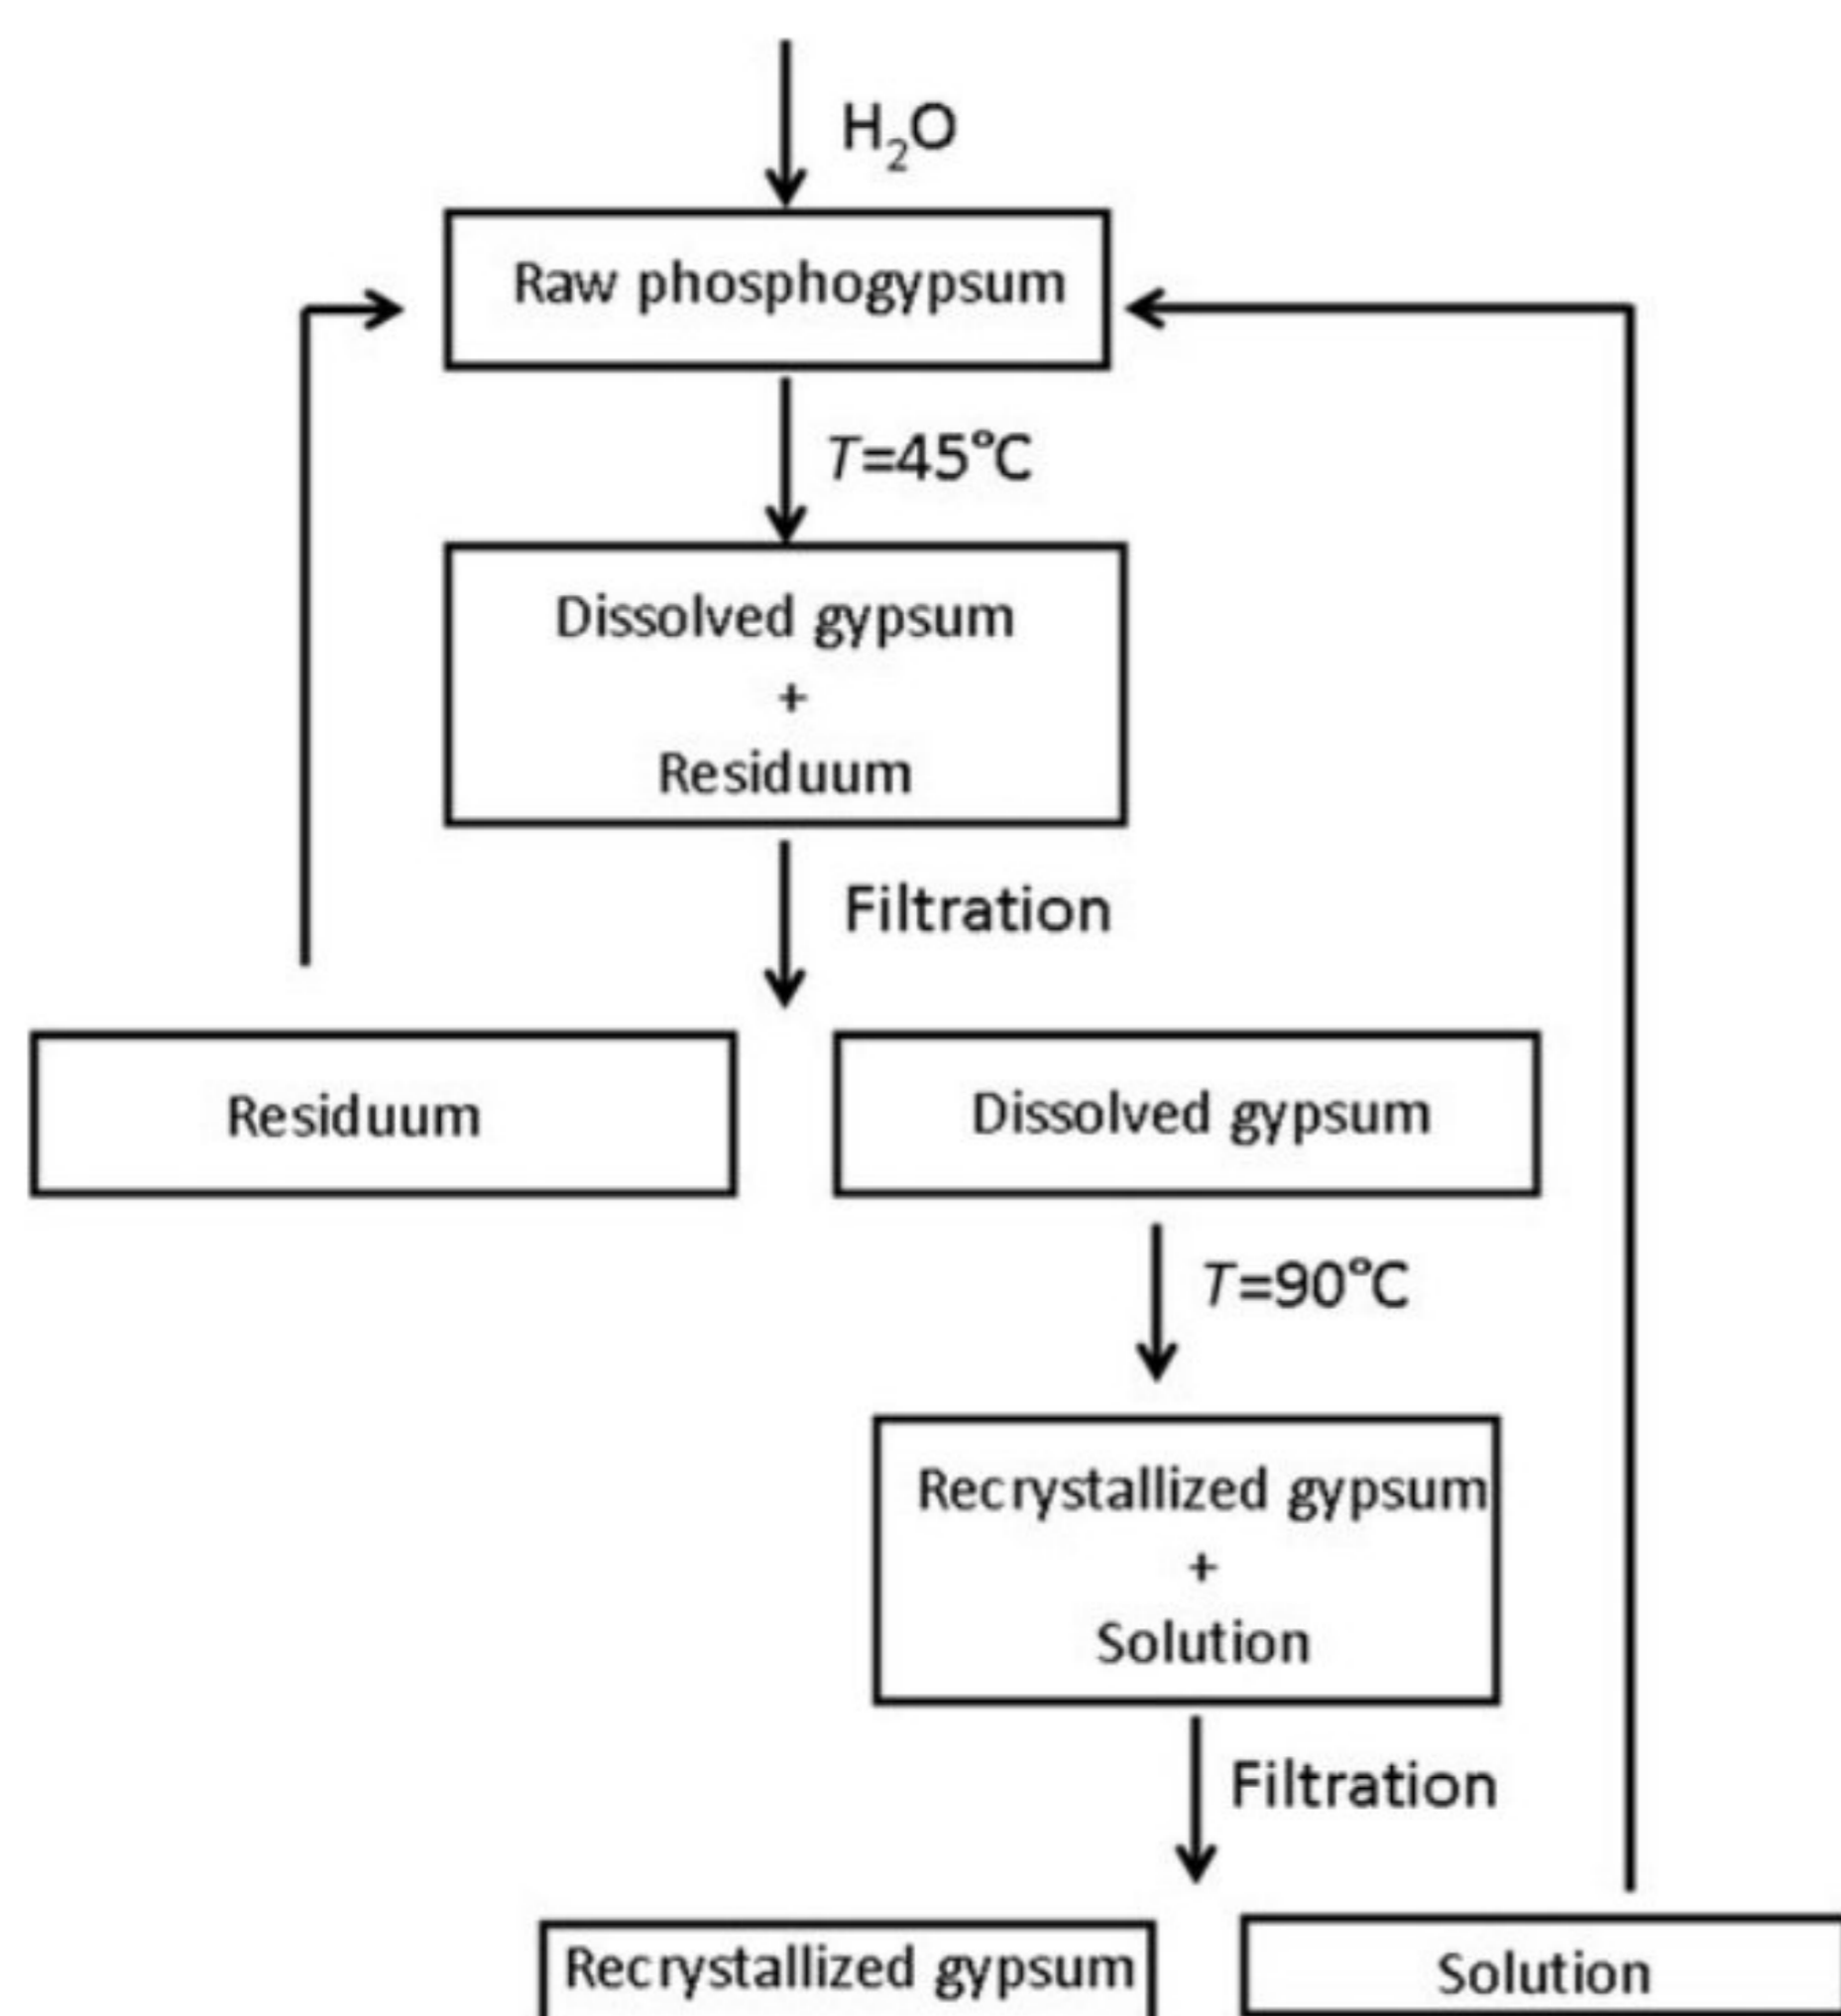


Fig. 2. Schematic overview of the recrystallization process.

### Inductively coupled plasma optical emission spectrometry measurements

The chemical compositions of the PG1 and PG1P samples were determined using inductively coupled plasma optical emission spectrometry (ICP-OES) with a Thermo Scientific iCAP 6500 Duo ICP-OES spectrometer (Thermo Fisher Scientific, UK) equipped with a RACID86 charge injector device (CID) detector. The detection limit for the elements analysed was  $\sim 0.1 \text{ mg L}^{-1}$ . The digestion was performed in an Advanced Microwave Digestion System (ETHOS 1, Milestone, Italy) using an HPR-1000/10S high-pressure segmented rotor.

### X-ray diffraction measurements

Mineralogical composition was determined using a Philips PW 1710 automated diffractometer, using Cu-K $\alpha$  radiation ( $\lambda = 1.54184 \text{ \AA}$ ) on randomly oriented powders in the range  $4\text{--}60^\circ 2\theta$  with a scanning step of  $1^\circ \text{ min}^{-1}$ . The tube current was set to 30 mA and the voltage to 40 kV. The identification of mineral phases followed the criteria recommended by Mikheev (1957) and the Joint Committee for Powder Diffraction Standards (JCPDS).

### Whiteness index

In order to compare the quality of the samples for utilization in the construction industry, the whiteness index (WI) values of raw phosphogypsum and recrystallized gypsum were measured. The WI was determined from the luminous reflectance, as described by Milošević & Logar (2017).

### Radiometric measurements

For the activity concentration determination, the samples were placed in  $120 \text{ cm}^3$  cylindrical plastic containers. Sealing was

performed to achieve radioactive equilibrium within the natural radioactive series for a period of 4 weeks. The activity concentration of radionuclides was determined using a high-purity germanium radiation detector of 50% relative efficiency. The detector was calibrated using a secondary reference material with a charcoal matrix in the same  $120 \text{ cm}^3$  cylindrical geometry (Pantelić *et al.*, 2015), spiked with standard radioactive solution ERX 9031-OL-427/12 (Czech Metrology Institute, Inspectorate for Ionizing Radiation). The radioactive solution contained  $^{241}\text{Am}$ ,  $^{109}\text{Cd}$ ,  $^{139}\text{Ce}$ ,  $^{57}\text{Co}$ ,  $^{60}\text{Co}$ ,  $^{137}\text{Cs}$ ,  $^{203}\text{Hg}$ ,  $^{113}\text{Sn}$ ,  $^{85}\text{Sr}$ ,  $^{88}\text{Y}$  and  $^{210}\text{Pb}$  radionuclides with energies that ranged from 46.5 to 1898 keV and with a total activity of 72.4 kBq at the reference date of 31 August 2012. The samples of raw phosphogypsum were measured twice, before and after the sealing of the samples' containers, and the purified gypsum sample was measured once, after the container was sealed.

By applying the  $\gamma$ -spectrometry method, the activity concentration of  $^{238}\text{U}$  was determined from its decay products  $^{234}\text{Th}$  (63 keV) and/or  $^{234\text{m}}\text{Pa}$  (1000 keV). The decay products of  $^{226}\text{Ra}$ ,  $^{214}\text{Bi}$  (609, 1120 and 1764 keV) and  $^{214}\text{Pb}$  (295 and 352 keV) were used for activity determination. The activity of  $^{232}\text{Th}$  was calculated using its daughter product  $^{228}\text{Ac}$  (338 and 911 keV).  $^{40}\text{K}$  was determined from its single line of 1460 keV  $\gamma$ -energy. The background spectrum was recorded regularly before or after sample counting. The measurement time was 60,000 s. The measurement uncertainty was  $\sim 10\%$ .

For uniformity in exposure estimates, the radionuclide concentrations have been defined in terms of radium equivalent activity ( $\text{Ra}_{\text{eq}}$ ) in  $\text{Bq kg}^{-1}$ . This allows a comparison of the activity concentrations of materials containing various amounts of  $^{226}\text{Ra}$ ,  $^{232}\text{Th}$  and  $^{40}\text{K}$  according to Eq. (1) (UNSCEAR, 2000):

$$\text{Ra}_{\text{eq}} = C_{\text{Ra}} + 143 \cdot C_{\text{Th}} + 0.077 \cdot C_{\text{K}} \quad (1)$$

where  $C_{\text{Ra}}$ ,  $C_{\text{Th}}$  and  $C_{\text{K}}$  are the activity concentrations of  $^{226}\text{Ra}$ ,  $^{232}\text{Th}$  and  $^{40}\text{K}$  in  $\text{Bq kg}^{-1}$ , respectively. The limit for  $\text{Ra}_{\text{eq}}$  is  $370 \text{ Bq kg}^{-1}$ , set by the report of the Organisation for Economic Co-operation and Development (OECD, 1979).

To assess the radiological hazard associated with the investigated samples of phosphogypsum, the  $\gamma$  index for construction materials was calculated using Eq. (2) (RS Official Gazette, 2018):

$$I_{\gamma} = \frac{C_{\text{Ra}}}{\text{MPC}(\text{Ra})} + \frac{C_{\text{Th}}}{\text{MPC}(\text{Th})} + \frac{C_{\text{K}}}{\text{MPC}(\text{K})} \quad (2)$$

where  $C_{\text{Ra}}$ ,  $C_{\text{Th}}$  and  $C_{\text{K}}$  are the measured concentrations and MPC (Ra), MPC(Th) and MPC(K) are the maximum permissible concentrations of  $^{226}\text{Ra}$ ,  $^{232}\text{Th}$  and  $^{40}\text{K}$ , respectively. Equivalent values for building materials used for interior, exterior and civil engineering construction as a base for roads, playgrounds and other civil engineering constructions (under the overlay layer) are listed in Table 1.

In the present work, the  $\alpha$  index, used for the assessment of the excess  $\alpha$  radiation due to radon inhalation originating from the building materials, was determined using Eq. (3) (Pantelić *et al.*, 2015):

$$I_{\alpha} = \frac{C(^{226}\text{Ra})}{200} \quad (3)$$

**Table 1.** Maximum permissible concentrations (MPCs) for  $^{226}\text{Ra}$ ,  $^{232}\text{Th}$  and  $^{40}\text{K}$  in building materials used for interiors, exteriors and in civil engineering construction.

Radionuclide	Label in Eq. (2)	Interiors (Bq kg <sup>-1</sup> )	Exteriors (Bq kg <sup>-1</sup> )	Civil engineering (Bq kg <sup>-1</sup> )
$^{226}\text{Ra}$	MPC(Ra)	300	400	700
$^{232}\text{Th}$	MPC(Th)	200	300	500
$^{40}\text{K}$	MPC(K)	3000	5000	8000

The external and internal hazard indices,  $H_{\text{ex}}$  and  $H_{\text{in}}$ , were defined using Eq. (4) and Eq. (5), respectively (UNSCEAR, 2000):

$$H_{\text{ex}} = \frac{C_{\text{Ra}}}{370} + \frac{C_{\text{Th}}}{259} + \frac{C_{\text{K}}}{4810} \quad (4)$$

$$H_{\text{in}} = \frac{C_{\text{Ra}}}{185} + \frac{C_{\text{Th}}}{259} + \frac{C_{\text{K}}}{4810} \quad (5)$$

The values of these indices should be <1, to indicate that the radiation hazard is insignificant.

## Results and discussion

### Chemical analysis

For each sample, three areas of  $\sim 5 \text{ mm}^2$  were analysed by SEM-EDS and the average results obtained are listed in Table 2. The PG1 and PG2 samples contain large amounts of Ca, S and O, as expected for the calcium sulfate-based material. The major impurity is Si, followed by small amounts of P, Al, Fe and Sr, which are typical of phosphogypsum from various deposits around the world (Jalali *et al.*, 2016; Zhou *et al.*, 2016; Kandil *et al.*, 2017).

The recrystallized PG1P sample is enriched in calcium sulfate, containing only small amounts of Al, Si and P. A more precise chemical analysis of the two samples was performed by ICP-OES, confirming the enrichment of Ca and S and the drastic depletion of Si and Fe after recrystallization (Table 3). These results support the effectiveness of recrystallization, which removed most of the slightly soluble impurities, which contain Si, Fe, Al, Ti, *etc.*, from phosphogypsum.

### XRD analysis

The XRD analysis showed that the most abundant phases in the PG1 and PG2 samples are gypsum ( $\text{CaSO}_4 \cdot 2\text{H}_2\text{O}$ ), brushite ( $\text{CaHPO}_4 \cdot 2\text{H}_2\text{O}$ ) and quartz (Fig. 3). These phases have also been identified in various phosphogypsum samples by various researchers (Roode & Strydom, 1999; Jalali *et al.*, 2016; Tian *et al.*, 2016). The XRD trace of PG1P is typical of pure gypsum (Fig. 3). The presence of other crystalline phases was not confirmed by XRD analysis, in accordance with the low levels of impurities obtained using SEM-EDS and ICP-OES elemental analyses. Specifically, in the PG1P sample, Al, Si and P calculated as oxides by stoichiometry amount to 1.02 wt.% in SEM-EDS analysis. In addition, 10 trace elements in ICP-OES analysis (Table 3) comprise 0.63 wt.%, which gives a low probability of detection in distinctive phase(s) by XRD analysis. The same applies for trace amounts of Na, Mg, Al, K, Ti, Fe, Sr and Ba in raw phosphogypsum (total 0.24 wt.% as oxides). The SEM-EDS,

**Table 2.** Chemical compositions (wt.%) of the samples investigated, obtained by SEM-EDS analysis.

Elements	PG1	PG2	PG1R	PG1P
O <sup>a</sup>	47.07	46.99	51.65	46.69
F	BDL	BDL	0.56	BDL
Na	BDL	BDL	0.08	BDL
Mg	BDL	BDL	0.03	BDL
Al	0.26	0.25	0.77	0.30
Si	2.23	2.25	41.19	0.06
P	0.34	0.31	0.65	0.14
S	21.77	21.67	1.15	22.86
K	BDL	BDL	0.07	BDL
Ca	28.13	28.37	2.13	29.95
Ti	BDL	BDL	0.22	BDL
Fe	0.15	0.16	1.34	BDL
Sr	0.04	BDL	BDL	BDL
Ba	BDL	BDL	0.15	BDL
Total	100.00 <sup>b</sup>	100.00	100.00	100.00


<sup>a</sup>Calculated by stoichiometry.

<sup>b</sup>Quantitative results normalized to 100%.  
BDL = below detection limit.


**Table 3.** Chemical compositions of the samples investigated, obtained by ICP-OES analysis.

Elements	Units	PG1	PG1P
Na	ppm	94.54	14.52
Mg	ppm	18.70	0.24
Al	ppm	260.05	12.55
Si	ppm	3529.07	74.63
P	ppm	2904.80	2426.13
S	wt.%	18.687	20.295
K	ppm	67.44	22.51
Ca	wt.%	25.049	27.508
Ti	ppm	121.44	36.96
Fe	ppm	605.15	24.24
Sr	ppm	412.99	374.42
Ba	ppm	94.81	6.45


ICP-OES and XRD results confirmed that calcium sulfate dihydrate is the principal phase present in raw phosphogypsum samples, which is formed according to the chemical reaction in Eq. (6):

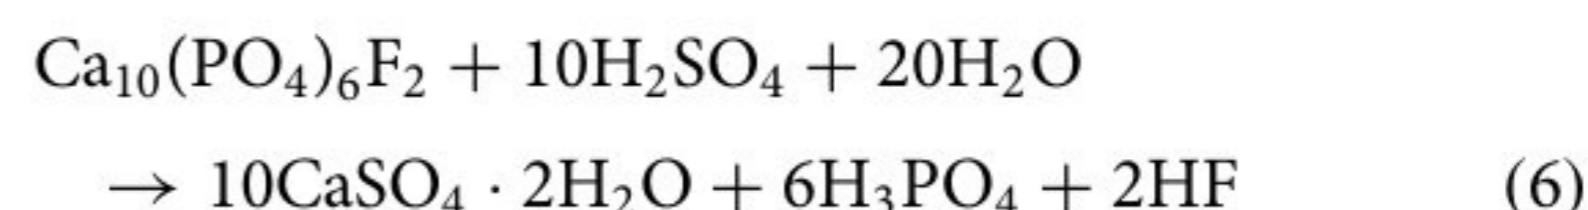


Quartz is the predominant Si-bearing phase, originating from the parent phosphate rock, as well as being precipitated by acid digestion of natural silicates and aluminosilicates. A relatively significant amount of phosphorus in raw phosphogypsum is present in the form of brushite, as was confirmed by XRD patterns (Roode & Strydom, 1999). Brushite formed similarly to gypsum, which is not surprising as these are isostructural mineral phases (see Eq. (7)) (Mikheev, 1957):

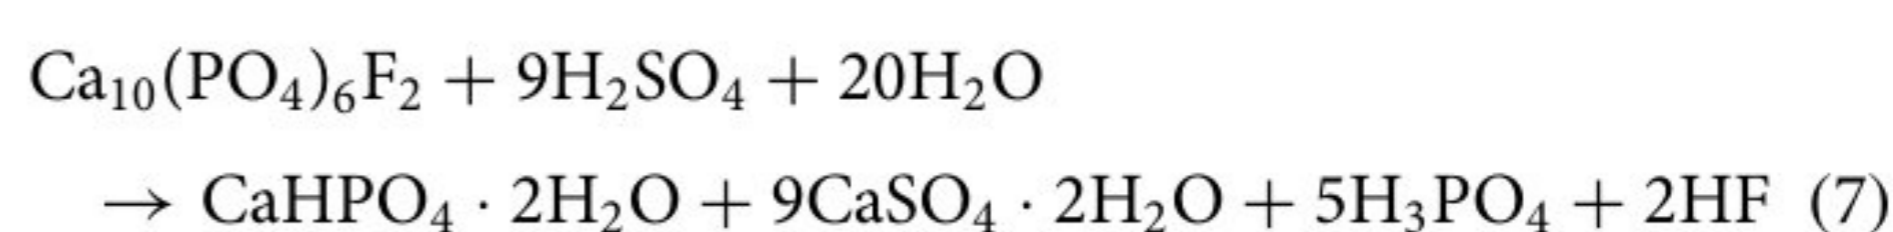

During acid digestion of aluminosilicate minerals,  $\text{Al}^{3+}$  ions are first released and then chemically bonded in synthetic

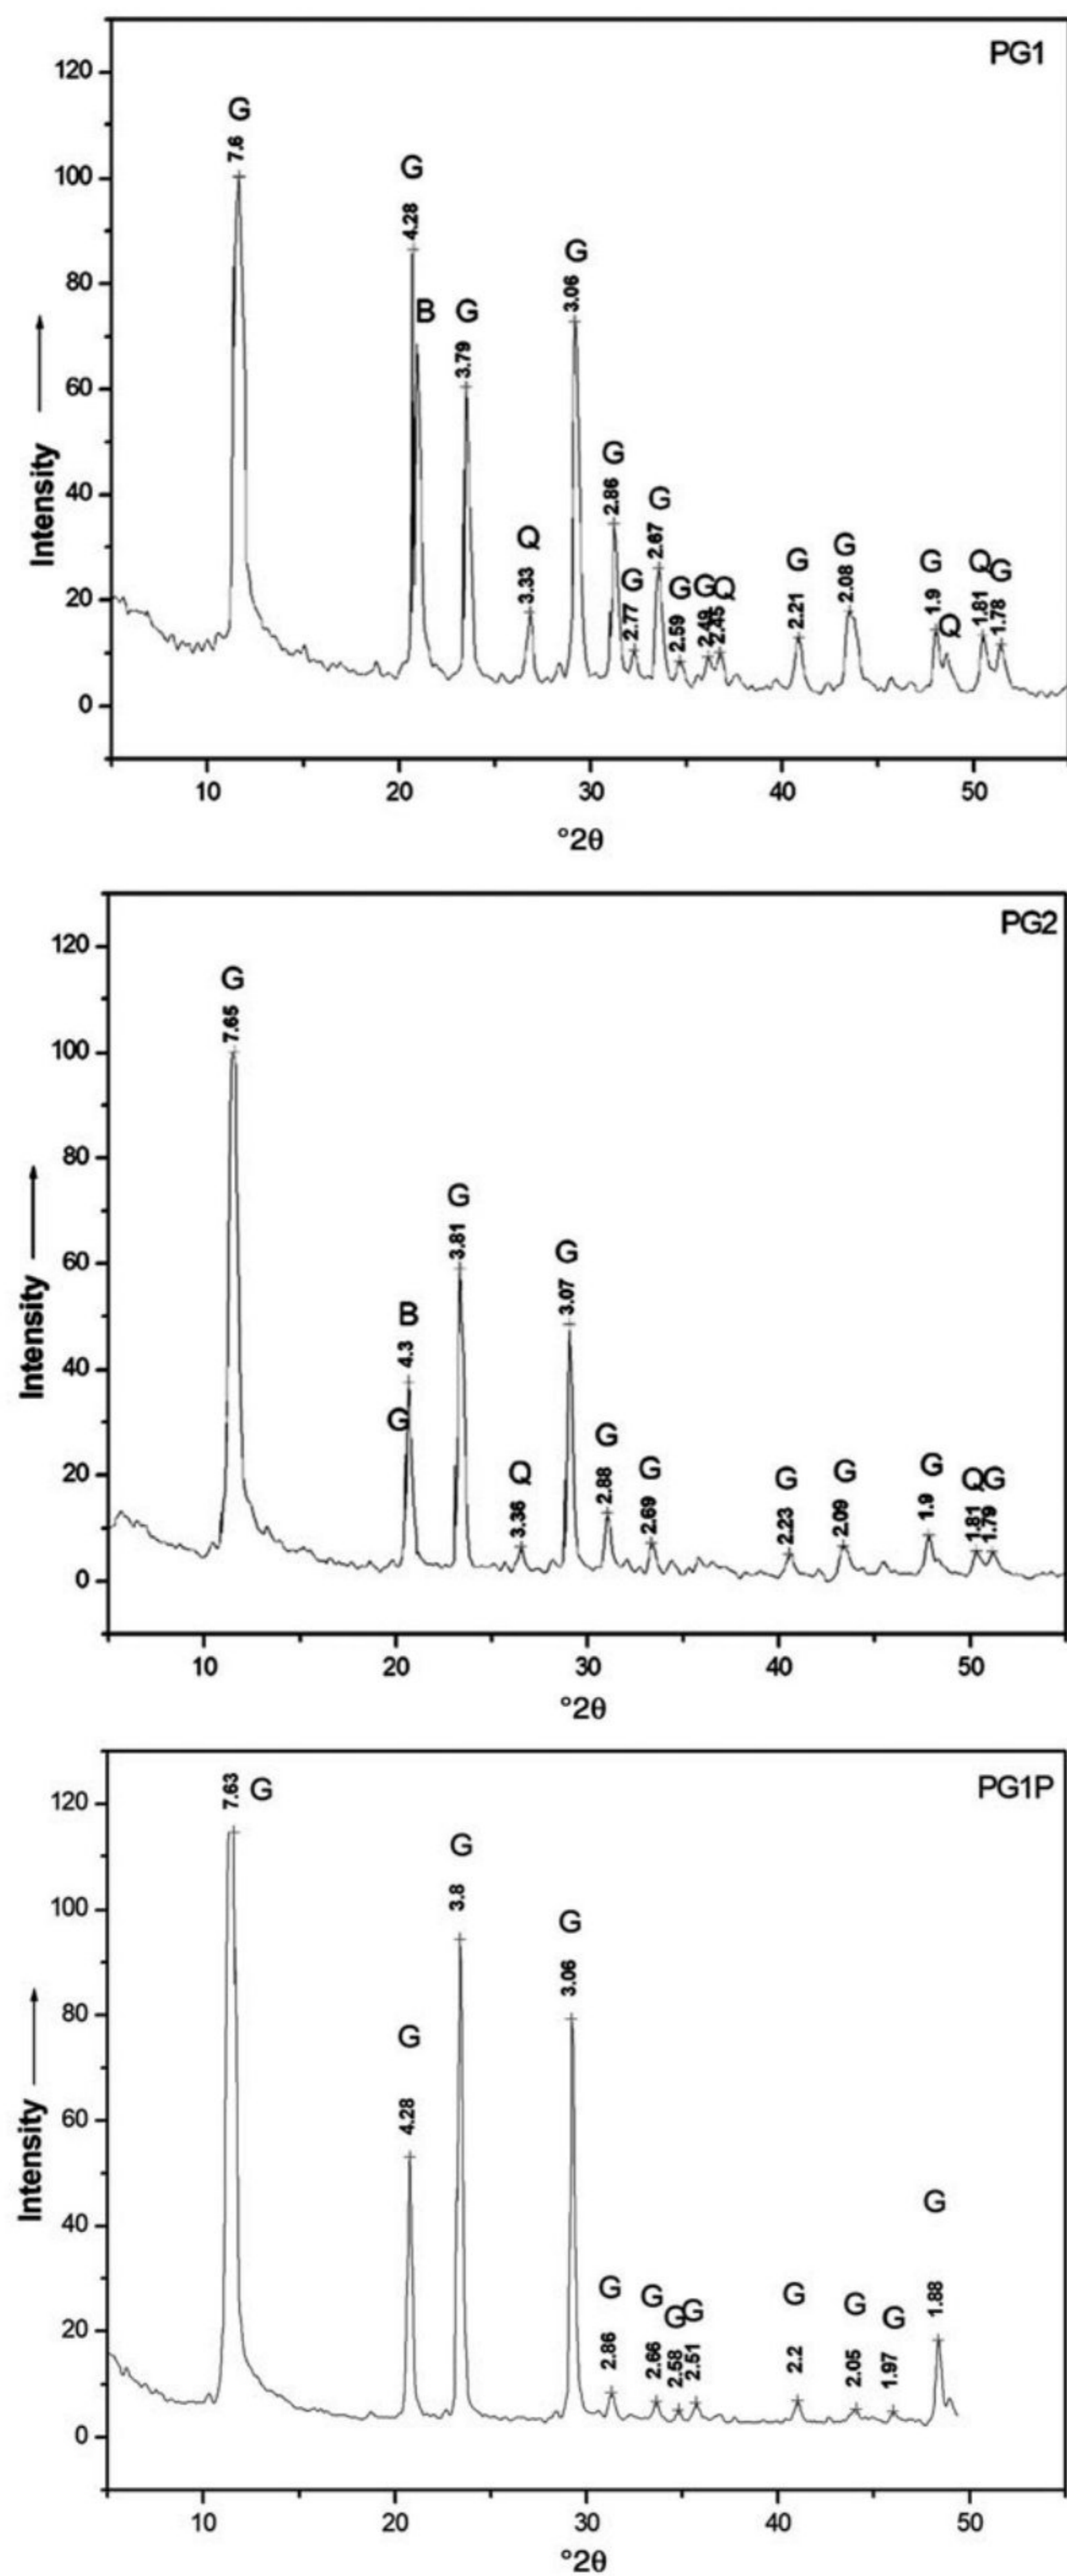


**Fig. 3.** XRD traces of investigated samples. The numbers correspond to the  $d$ -spacings of the main diffraction maxima (Å) of the phases present. B = brushite; G = gypsum; Q = quartz.

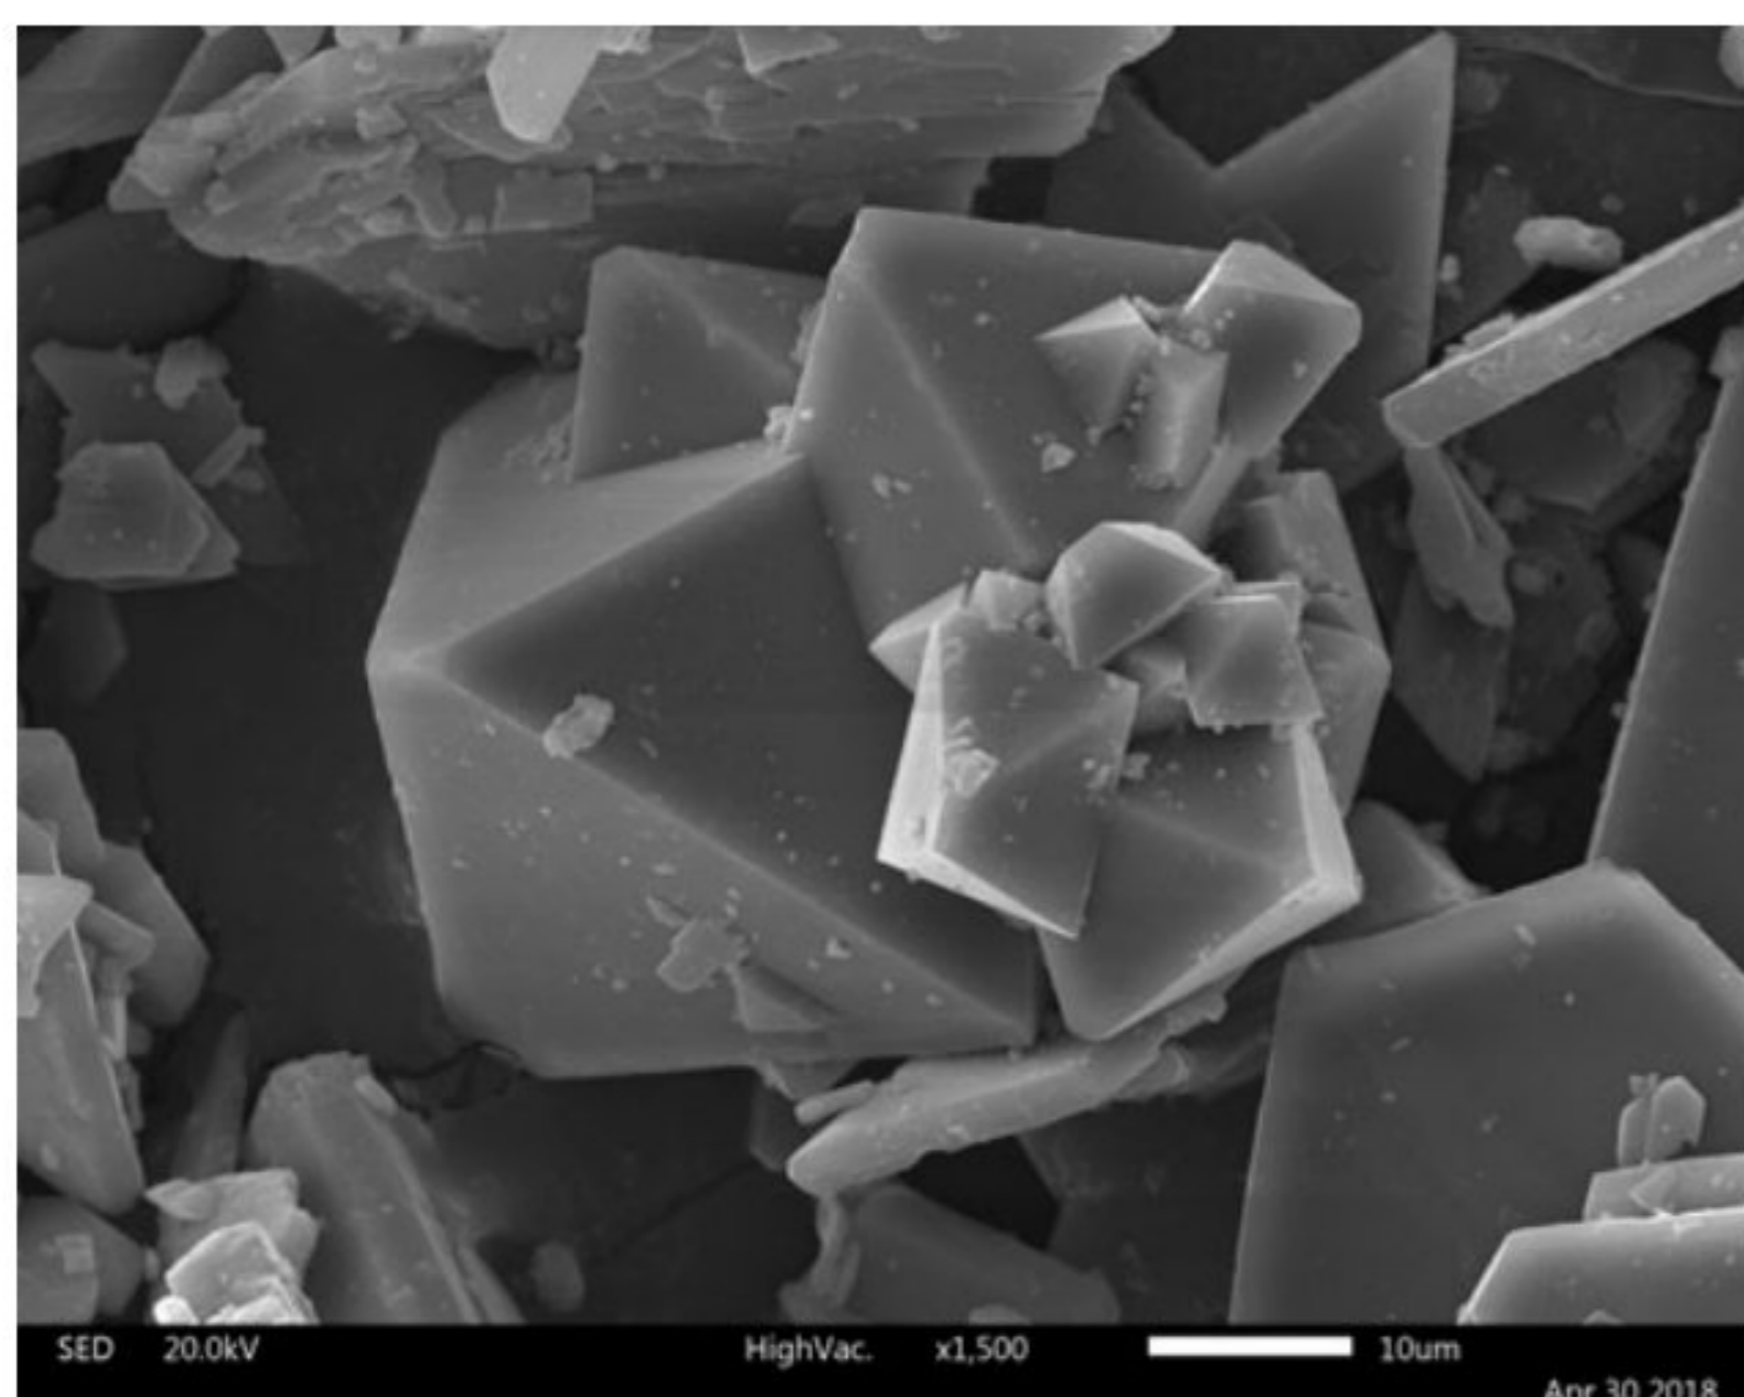

**Fig. 4.** SEM image of mineral chukhrovite. Scale bar: 10  $\mu\text{m}$ .

chukhrovite ( $\text{Ca}_{4.5}\text{Al}_2(\text{SO}_4)\text{F}_{13}\cdot 12\text{H}_2\text{O}$ ) (Fig. 4), according to the reaction in Eq. (8):

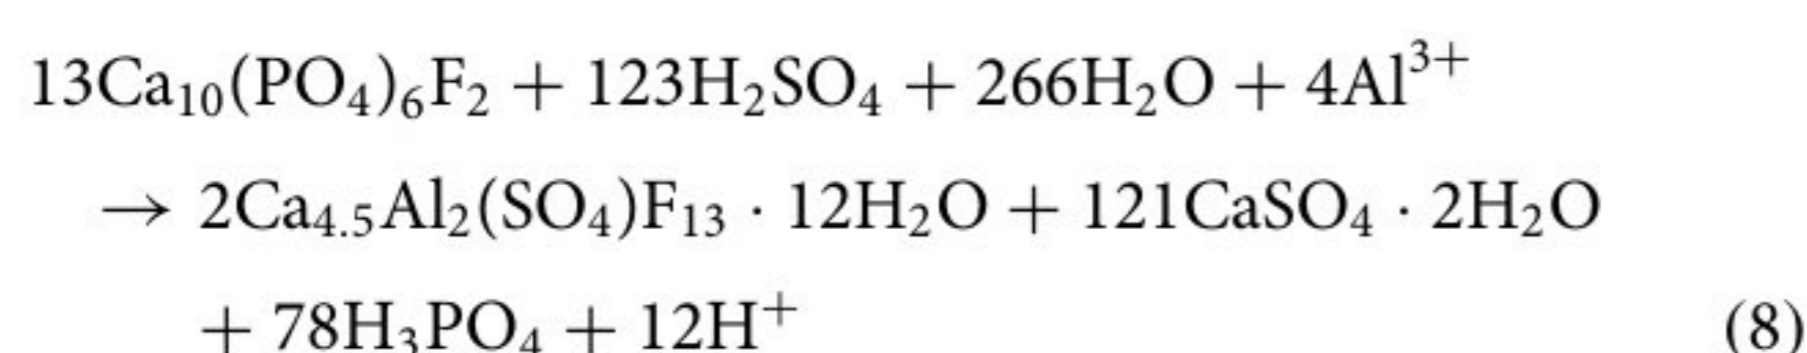

On the other hand, phosphogypsum was purified to a significant extent after the recrystallization process. Quartz and some other impurities (such as Ba in  $\text{BaSO}_4$ , Ra in  $\text{RaSO}_4$ , Ti in hydrated  $\text{TiO}_2$ , Al in chukhrovite, Fe in ferric oxyhydroxide species, *etc.*), due to their poor solubility, remained in the insoluble residue, while highly soluble ions ( $\text{Na}^+$ ,  $\text{K}^+$ ,  $\text{Mg}^{2+}$ ) tended to concentrate in the supernatant. Although the solubility of brushite is a twelfth of that of gypsum, the recrystallization did not affect significantly the phosphorus content. This may be indicative of: (1) other P-bearing phases being present; (2) replacement of  $\text{SO}_4^{2-}$  with  $\text{HPO}_4^{2-}$  within the crystal structure of gypsum; or (3) shifting of the  $\text{HPO}_4^{2-} + \text{H}_2\text{O} \leftrightarrow \text{H}_2\text{PO}_4^- + \text{OH}^-$  equilibrium in the neutral water solution to the left compared to the highly acidic conditions of phosphate rock digestion with  $\text{H}_2\text{SO}_4$ . ( $\text{Ca}(\text{H}_2\text{PO}_4)_2$  has 100 times greater solubility than the less acidic  $\text{CaHPO}_4\cdot 2\text{H}_2\text{O}$  form.)

### SEM analysis

The SEM analysis revealed a significant increase in the gypsum crystal size after the recrystallization (Fig. 5). Moreover, the  $z/x$  axis ratio increased from 1–3 to  $>5$  for raw and recrystallized samples, respectively, producing long-bladed crystals. Stable laboratory conditions (temperature of  $90^\circ\text{C}$ , no stirring) promoted such crystal growth. A similar result was obtained with calcium sulfate whiskers synthesized from flue gas desulfurization of gypsum using the atmospheric acidification method (Sun *et al.*, 2016).

### Whiteness index

The WI of 52.5%, determined for raw phosphogypsum (PG1), is too low for potential use in some industries (a value of 100%

corresponds to a pure white colour). An increase of the WI to 80.5% after the recrystallization is in accordance with the ICP-OES and SEM-EDS analyses, which showed a significantly smaller Fe content in the purified gypsum. This increase in the WI benefits the potential use of recrystallized phosphogypsum in various industries. For example, in the Serbian cement industry, A-grade cements should have WI values  $>80\%$ , so for gypsum to be used as one of the components of A-grade cements, it must comply with this standard (RS Official Gazette, 2014). Furthermore, chiefly high-strength gypsum of high whiteness is applied for interior decoration (Lushnikova & Dvorkin, 2016).

### Activity concentration measurements

The phosphogypsum samples were analysed by means of  $\gamma$ -spectrometry to quantify radioactivity concentrations using a high-purity germanium detector. The results obtained are presented in Table 4. Similar phosphogypsum activity levels for the radionuclides  $^{238}\text{U}$ ,  $^{226}\text{Ra}$ ,  $^{232}\text{Th}$  and  $^{40}\text{K}$  have also been reported in other studies (Sahu *et al.*, 2014; Jung *et al.*, 2017). The activity concentration values for natural radionuclides before and after the sealing of the samples' containers were within experimental uncertainty of the measurements, except in the case of  $^{238}\text{U}$  and  $^{40}\text{K}$  (Table 4). This is in accordance with the work of Ji *et al.* (2017), who reported that in chemically processed materials such as phosphogypsum,  $^{226}\text{Ra}$  may be accurately quantified in hermetically sealed samples using  $\gamma$ -spectrometry, but not  $^{238}\text{U}$ .


Further analysis showed that after the recrystallization process, the activity concentration of  $^{226}\text{Ra}$  decreased by approximately five- to six-fold, and for other natural nuclides, their activity concentrations were below the minimum detectable level. During recrystallization, all radionuclides precipitated in the insoluble residue due to their poor solubility. In addition, the main radiation risk of the investigated samples comes from  $^{226}\text{Ra}$  activity concentrations, which could be accurately determined using  $\gamma$ -spectrometry without attaining secular equilibrium.

The results of the radiological hazard assessments are listed in Table 5. The calculated values for the PG1 and PG2 samples were greater than the limiting values for  $\text{Ra}_{\text{eq}}$  ( $>370 \text{ Bq kg}^{-1}$ ), the  $\alpha$  index ( $I_\alpha > 1$ ), the external hazard index ( $H_{\text{ex}} > 1$ ) and the internal hazard index ( $H_{\text{in}} > 1$ ). Those values were approximately twice as high the maximum values recorded after measurement of 265 gypsum samples used as building materials in Serbia (260, 1.30, 0.70 and 1.41 for  $\text{Ra}_{\text{eq}}$ ,  $I_\alpha$ ,  $H_{\text{ex}}$  and  $H_{\text{in}}$ , respectively) (Pantelić *et al.*, 2015). After recrystallization, all of the calculated values decreased significantly (Table 5), being three to five times smaller than the maximum values of building materials (Pantelić *et al.*, 2015).

According to the  $\gamma$ -indices, with limiting values  $<1$ , the PG1 and PG2 samples should be rejected as materials for exterior and interior usage (Table 5) and may be used only in civil engineering construction as a base for roads, playgrounds and other civil engineering constructions. On the other hand, the PG1P sample, obtained after the recrystallization process, met all of the radiological hazard criteria associated with construction materials and can be used safely in construction projects.

### Summary and conclusion

Two samples of phosphogypsum, obtained from the waste landfills of the chemical company Elixir Prahovo (Serbia), are

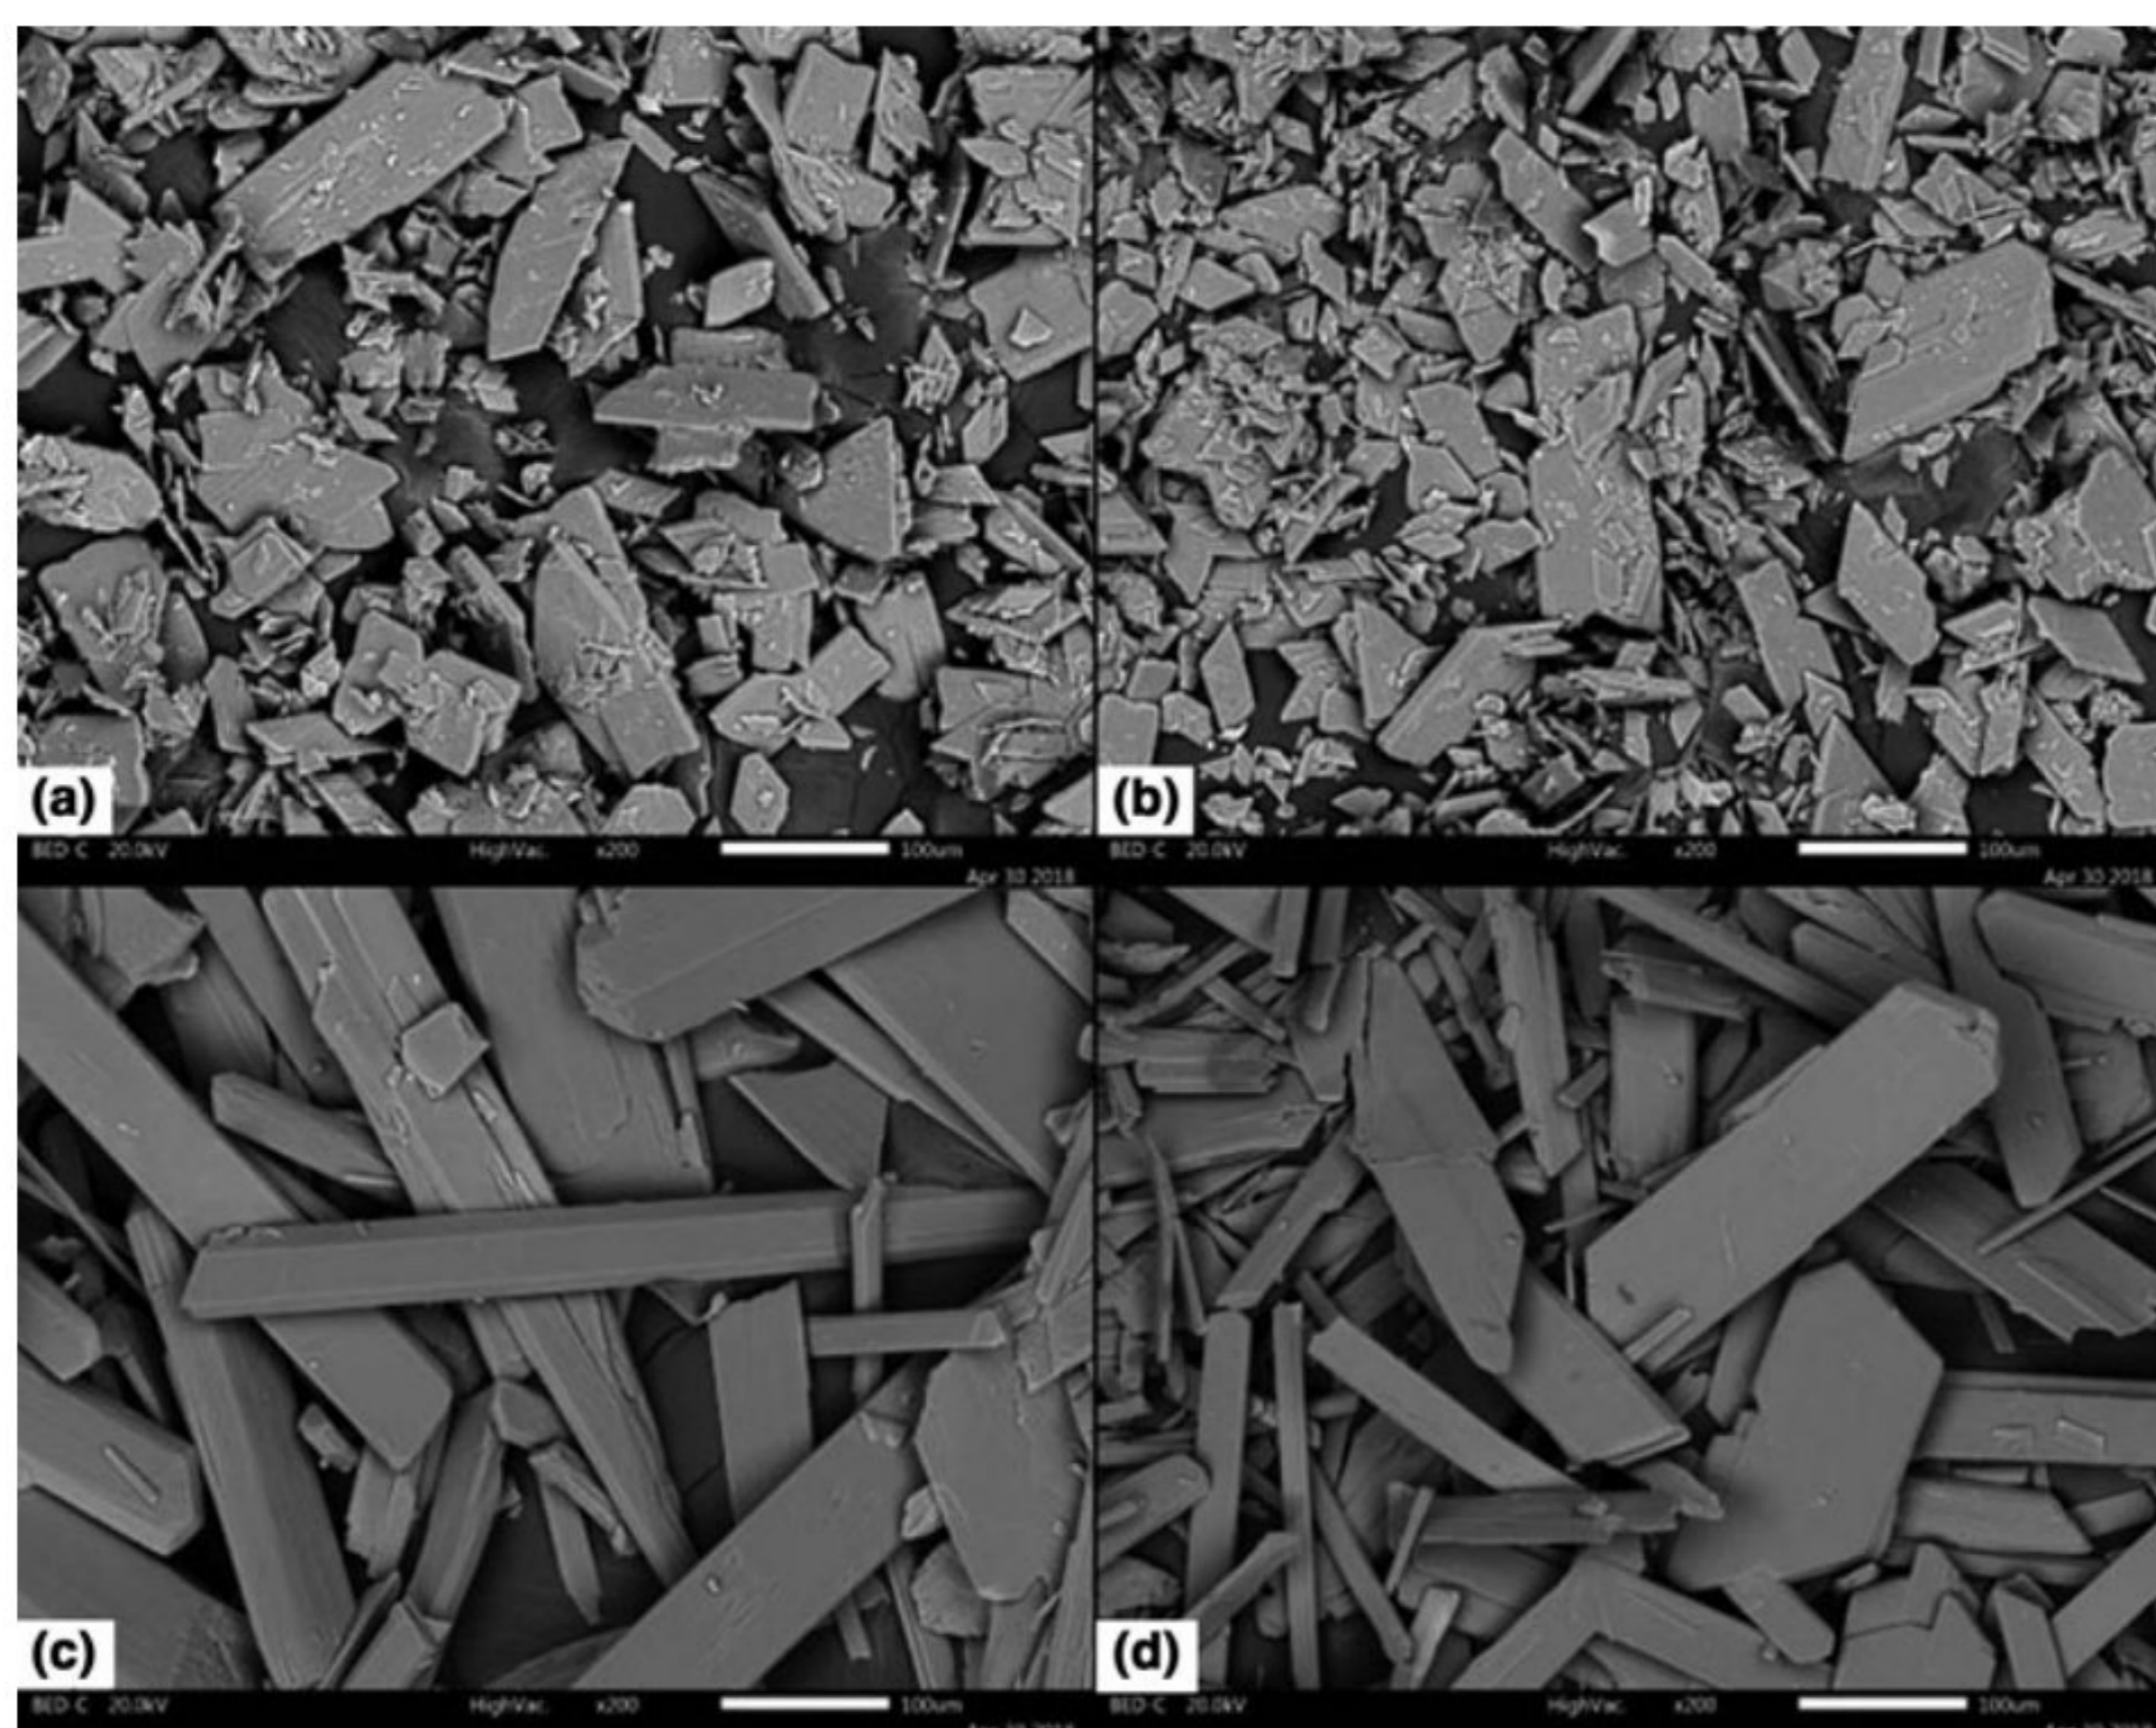

**Fig. 5.** SEM images of (a) PG1, (b) PG2 and (c,d) PG1P. Scale bars: 100 µm.

**Table 4.** Activity concentration values of phosphogypsum samples (PG1 and PG2) and purified gypsum (PG1P).

	PG1 <sup>a</sup> (Bq kg <sup>-1</sup> )	PG1 (Bq kg <sup>-1</sup> )	PG2 <sup>a</sup> (Bq kg <sup>-1</sup> )	PG2 (Bq kg <sup>-1</sup> )	PG1P (Bq kg <sup>-1</sup> )
<sup>238</sup> U	140 ± 30	100 ± 20	160 ± 30	<7	<30
<sup>235</sup> U	5.7 ± 0.4	3.7 ± 0.3	6.4 ± 0.4	5.6 ± 0.4	<2
<sup>226</sup> Ra	440 ± 20	480 ± 30	520 ± 30	500 ± 30	82 ± 8
<sup>210</sup> Pb	270 ± 30	300 ± 40	360 ± 40	340 ± 40	<40
<sup>232</sup> Th	<1	<2	10 ± 3	7 ± 2	<7
<sup>40</sup> K	18 ± 6	<9	40 ± 8	<9	<20

<sup>a</sup>Samples measured before the sealing of sample container.

dominated by Ca and S in the form of calcium sulfate dihydrate (*i.e.* gypsum; CaSO<sub>4</sub>·2H<sub>2</sub>O). The major impurity is represented by Si in the form of quartz. After applying a recrystallization process, the purified gypsum obtained was composed of very pure calcium sulfate dihydrate, containing only small amounts of phosphorus. There was a substantial increase in the gypsum crystal size, yielding a long-bladed crystal habit with an improved WI.

Based on  $\gamma$ -spectroscopic analysis, the mean activity concentrations of <sup>238</sup>U and <sup>226</sup>Ra in raw phosphogypsum samples are greater than the international recommended limits, while the opposite result was obtained for recrystallized gypsum.

For both phosphogypsum samples, the calculated values for Ra<sub>eq</sub>, the  $\alpha$ -index and almost all  $\gamma$ -indices were higher than the international recommended limits, except for the  $\gamma$ -index limit calculated for utilization in road construction. On the other hand, all of the calculated indices for the recrystallized gypsum were lower than the recommended limits. Therefore, the recrystallized gypsum satisfies all of these requirements and presents no radiation hazard when used as a building material, while raw phosphogypsum from the Elixir Prahovo waste landfills can be directly used only as a road construction material.

**Table 5.** Ra<sub>eq</sub>, I<sub>α</sub>, H<sub>ex</sub>, H<sub>in</sub> and I<sub>γ</sub> values calculated for phosphogypsum samples (PG1 and PG2) and purified gypsum (PG1P).

Index	PG1 <sup>a</sup>	PG1	PG2 <sup>a</sup>	PG2	PG1P
Ra <sub>eq</sub> (Bq kg <sup>-1</sup> )	441	480	537	510	82
I <sub>α</sub> (Bq kg <sup>-1</sup> )	2.20	2.40	2.60	2.50	0.41
H <sub>ex</sub> (Bq kg <sup>-1</sup> )	1.19	1.30	1.45	1.38	0.22
H <sub>in</sub> (Bq kg <sup>-1</sup> )	2.38	2.59	2.86	2.73	0.44
I <sub>γE</sub> (exterior)	1.10	1.20	1.34	1.27	0.21
I <sub>γI</sub> (interior)	1.47	1.60	1.80	1.70	0.27
I <sub>γR</sub> (road)	0.63	0.69	0.77	0.73	0.12

<sup>a</sup>Samples measured before the sealing of sample container.

**Acknowledgements.** The authors are grateful to Professor George Christidis, Principal Editor of *Clay Minerals*, and three reviewers for their constructive suggestions and corrections, which greatly improved the paper. The authors are also grateful to Dobrila Nikolić, MA in English, for language and style corrections and to the chemical company Elixir Prahovo for providing the samples for analysis.

**Financial support.** The research was supported by the Ministry of Education, Science and Technological Development of the Republic of Serbia through Project No. 176010 and Project No. 43007.

## References

- Amjad Z. (1988) Calcium sulfate dihydrate (gypsum) scale formation on heat exchanger surfaces: the influence of scale inhibitors. *Journal of Colloid and Interface Science*, **123**(2), 523–536.
- Azimi G. (2010) *Evaluating the Potential of Scaling Due to Calcium Compounds in Hydrometallurgical Processes*. PhD thesis, Department of Chemical Engineering and Applied Chemistry, University of Toronto, Toronto, Canada.
- Cánovas C.R. (2018) Valorization of wastes from the fertilizer industry: current status and future trends. *Journal of Cleaner Production*, **174**, 678–690.
- Costa C., Fortes A., Rocha F., Cerqueira A., Santos D. & Amaral M.H. (2019) Characterization of Portuguese gypsums as raw materials for dermo-cosmetics. *Clay Minerals*, **54**, 277–281.



- Elixir Prahovo (2018) About the company. Retrieved from <https://www.elixirprahovo.rs/en/about-the-company-2> (accessed 5 May 2018).
- Hammam I., Horchani-Naifer K. & Férid M. (2013) Characterization and optical study of phosphogypsum industrial waste. *Studies in Chemical Process Technology*, **1**, 30–36.
- Hua S, Wang K. & Yao X. (2016) Developing high performance phosphogypsum-based cementitious materials for oil-well cementing through a step-by-step optimization method. *Cement and Concrete Composites*, **72**, 299–308.
- IAEA (2013) *Radiation Protection and Management of NORM Residues in the Phosphate Industry*. Safety Reports Series No. 78. International Atomic Energy Agency, Vienna, Austria, 288 pp.
- Jalali J., Magdich S., Jarboui R., Loungou M. & Ammar E. (2016) Phosphogypsum biotransformation by aerobic bacterial flora and isolated *Trichoderma asperellum* from Tunisian storage piles. *Journal of Hazardous Materials*, **308**, 362–373.
- Ji Y.Y., Lim J.M., Kim H., Kim C.J., Lim C.S. & Chung K.H. (2017) Limitations of gamma-ray spectrometry in the quantification of  $^{238}\text{U}$  and  $^{232}\text{Th}$  in raw materials and by-products. *Journal of Radioanalytical and Nuclear Chemistry*, **311**(2), 1163–1168.
- Jung Y., Lim J.M., Ji Y.Y., Chung K.H. & Kang M.J. (2017) The transport characteristics of  $^{238}\text{U}$ ,  $^{232}\text{Th}$ ,  $^{226}\text{Ra}$ , and  $^{40}\text{K}$  in the production cycle of phosphate rock. *Journal of Radiation Protection and Research*, **42**(1), 33–41.
- Kandil A.H.T., Cheira M.F., Gado H.S., Soliman M.H. & Akl H.M. (2017) Ammonium sulfate preparation from phosphogypsum waste. *Journal of Radiation Research and Applied Sciences*, **10**, 24–33.
- Lushnikova N. & Dvorkin L. (2016) Sustainability of gypsum products as a construction material. Pp. 643–681 in *Sustainability of Construction Materials*, 2nd edition (Jamal Khatib, editor). Woodhead Publishing, Cambridge, UK.
- Mikheev V.I. (1957) *Rentgenometricheskii opredelitel mineralov (X-Ray Determination of Minerals)*. Gosudarstvennoe nauchno-tehnicheskoe izdatelstvo literatur po geologii i ohrane nedr, Moscow, USSR, 868 pp. (in Russian).
- Milošević M. & Logar M. (2017) Properties and characterization of a clay raw material from Miličinica (Serbia) for use in the ceramic industry. *Clay Minerals*, **52**, 329–340.
- Moreira R.H., Queiroga F.S., Paiva H.A., Medina N.H., Fontana G. & Guazzelli M.A. (2018) Extraction of natural radionuclides in TENORM waste phosphogypsum. *Journal of Environmental Chemical Engineering*, **6**, 6664–6668.
- OECD (1979) *Exposure to Radiation from the Natural Radioactivity in Building Materials*. Report by an NEA Group of Experts. Organisation for Economic Co-operation and Development, Paris, France, 40 pp.
- Pantelić G.K., Todorović D.J., Nikolić J.D., Rajačić M.M., Janković M.M. & Sarap N.B. (2015) Measurement of radioactivity in building materials in Serbia. *Journal of Radioanalytical and Nuclear Chemistry*, **303**(3), 2517–2522.
- Pérez-López R, Macías F, Cánovas C.R., Sarmiento A.M. & Pérez-Moreno S.M. (2016) Pollutant flows from a phosphogypsum disposal area to an estuarine environment: an insight from geochemical signatures. *Science of the Total Environment*, **553**, 42–51.
- Rolnick L.S. (1954) *The Stability of Gypsum and Anhydrite in the Geologic Environment*. PhD thesis, Department of Geology, Massachusetts Institute of Technology, Cambridge, MA, USA.
- Roode Q.I. & Strydom C.A. (1999) The characterization of phosphogypsum and gypsum-brushite mixtures by X-ray diffraction, thermogravimetric and differential scanning calorimetric techniques. *Concrete Science and Engineering*, **1**, 222–227.
- RS Official Gazette (2014) *Rulebook on Cement Quality*. Official Gazette of the Republic of Serbia No. 44. National Assembly of the Republic of Serbia, Belgrade, Serbia, 11 pp. (in Serbian).
- RS Official Gazette (2018) *Rulebook on Limits of Radionuclides Content in Drinking Water, Foodstuffs, Feeding Stuffs, Medicines, General Use Products, Construction Materials and Other Goods That Are Put on Market*. Official Gazette of the Republic of Serbia No. 36. National Assembly of the Republic of Serbia, Belgrade, Serbia, 5 pp. (in Serbian).
- Sahu S.K., Ajmal P.Y., Bhangare R.C., Tiwari M. & Pandit G.G. (2014) Natural radioactivity assessment of a phosphate fertilizer plant area. *Journal of Radiation Research and Applied Sciences*, **7**(1), 123–128.
- Saueia C.H.R. (1998) *Caracterização Radioquímica do Fosfogesso e implicações radiológicas de sua utilização como material de construção. Dissertação*. PhD thesis. Instituto de Pesquisas Energéticas e Nucleares, Autarquia Associada à Universidade de São Paulo, São Paulo, Portugal (in Portuguese).
- Sun H., Tan D., Peng T. & Liang Y. (2016) Preparation of calcium sulfate whisker by atmospheric acidification method from flue gas desulfurization gypsum. *Procedia Environmental Sciences*, **31**, 621–626.
- Tian T., Yan Y., Hu Z., Xu Y., Chen Y. & Shi J. (2016) Utilization of original phosphogypsum for the preparation of foam concrete. *Construction and Building Materials*, **115**, 143–52.
- UNSCEAR (2000) *United Nations Scientific Committee on the Effects of Atomic Radiation. Sources and Effects of Ionizing Radiation*. United Nations Scientific Committee on the Effects of Atomic Radiation, New York, NY, USA, 659 pp.
- Walawalkar M., Nichol C.K. & Azimi G. (2016) Process investigation of the acid leaching of rare earth elements from phosphogypsum using HCl, HNO<sub>3</sub>, and H<sub>2</sub>SO<sub>4</sub>. *Hydrometallurgy*, **166**, 195–204.
- Zhou J., Sheng Z., Li T., Shu Z., Chen Y. & Wang Y. (2016) Preparation of hardened tiles from waste phosphogypsum by a new intermittent pressing hydration. *Ceramics International*, **42**, 7237–7245.